

# Computer Simulation of Fracture Process in Compressive Failure of Cross-Ply Laminate of Composite Materials

Takeaki Nadabe

Department of Advanced Energy, Graduate School of Frontier Sciences,  
The University of Tokyo, Kashiwa, Chiba, Japan  
E-mail: nadabe@smart.k.u-tokyo.ac.jp

**Abstract**—This study investigates computer simulation of fracture process in compressive failure of cross-ply laminate of composite materials. The purpose of this study is to establish numerical analysis method to understand fracture mechanism and predict mechanical response of composite materials through computer simulation. The reinforcement fibers in 0-degree plies are modeled by circle cross-section beam elements to represent the three-dimensional effect in bending of fibers. Cohesive elements are inserted in the connection of beam elements to simulate the bending breaking of fibers. For the purpose of parallel computing, the domain decomposition method is applied, and for pre-conditioned conjugate gradient algorithm, incomplete Cholesky conjugate gradient method is applied. The simulated results show that in the initial state of the loading, the stress concentration occurs around the initial misalignment of fiber in 0-degree plies, and it also occurs around the area where fibers come close in 90-degree plies. At average applied strain 1.20 %, the fiber breaking damage initiates in 0-degree ply, and after this point the damage develops in the material. The simulated damage is close to the microscope picture of the actual composite materials obtained in the experiment. The current simulation is considered to correspond with the actual material deformation.

**Keywords:** Computer Simulation, Fracture Mechanism, Composite Materials, Parallel Computing, Domain Decomposition Method

## INTRODUCTION

Composite materials commonly have complex internal structures including fibers, matrix, interfaces and interlaminar regions, and when precise evaluation of fracture strength of the material is conducted, the internal fracture process in the materials is necessary to be taken into account in the numerical analysis [1–3]. In recent years, the capability of computers has been extensively improved and the fracture mechanism of composite materials including crack propagation, interlaminar delamination and fiber/matrix interface decohesion are simulated using the computational capability [4]. Applying the computer simulation of fracture process of the material, the detail stress and strain distributions in the inside of the material are considered to be clarified, and several indications for improving the mechanical performance of the material are considered to be obtained [5–7]. This study investigates the computer simulation of fracture process in compressive failure of cross-ply laminate of composite materials. The purpose of this study is to establish the numerical analysis method to understand the fracture mechanism and predict the mechanical response of composite materials through the computer simulation.

## NUMERICAL MODEL

The numerical model is constructed for compressive failure of cross-ply laminate of composite material. Figure 1 illustrates the analysis model. Finite element method is used for the analysis. The stacking sequence of the laminate is [0/90]<sub>s</sub>. The white and gray elements in Fig. 1 represent fibers and matrix, respectively. The thickness of the ply in y-direction is 85  $\mu\text{m}$ . The length in x-direction is 200  $\mu\text{m}$ , and the thickness in z-direction is 100  $\mu\text{m}$ . The diameter of each fiber is set to 7.0  $\mu\text{m}$ , and the

interval of fibers is 10.0  $\mu\text{m}$ . The fiber volume fraction of the materials is set to 40.0 %, and there are 9 fibers in each 0-degree ply. In this analysis, in order to simulate the bending breaking of each fiber, the fibers in 0-degree plies are modeled by circle cross-section beam elements, and the cohesive elements are inserted in the connection of fiber beam elements. When the high bending deformation occurs in fiber beam elements, the cohesive elements open and the fiber bending breaking occurs in the analysis. The fiber beam elements applied in this analysis are the Timoshenko type beam elements and have three nodes and four integration points. The matrix in 0-degree plies and the fibers and matrix in 90-degree plies are modeled by two-dimensional plate elements. The plate elements have eight nodes and four integration points in order to avoid the shear locking and zero-energy mode deformation particularly in plastic deformation. The one fiber placed at the center in each 0-degree ply has the initial misalignment as shown in Fig. 1. The initial misalignment of the fiber is introduced using the sine function. The x coordinate of each node is placed regularly, and the y coordinate of each node is calculated using the sine function. Only the central part of this fiber has the misalignment and the other part of the fiber is modeled as the straight line. The other fibers in 0-degree plies are also modeled as the straight lines and the fiber axial direction is parallel to the x-direction. The periodic boundary condition is introduced in both edge of the laminate to avoid the edge fracture of the material.

Due to the atomic structure in the inside of the fibers, the fibers commonly have the different material property in between fiber axial and transverse directions. Here, the fibers are modeled by the transversely isotropic elastic material. Table 1 shows the material property of the fibers. Carbon fiber AS4 (Hexcel Corp.) is assumed [8]. Matrix is modeled by isotropic elastic-plastic material.

Commonly the compressive failure of composite materials is affected by the nonlinear stress-strain relation of matrix, thus in this analysis the nonlinear stress-strain curve of matrix shown in Fig. 2 is applied, and the nonlinear finite element analysis is conducted. Table 2

shows the material property of matrix. Epoxy resin 3501-6 (Hercules Chemical Company, Inc.) is assumed [8]. The quasi-static and room temperature environment are assumed in the analysis.

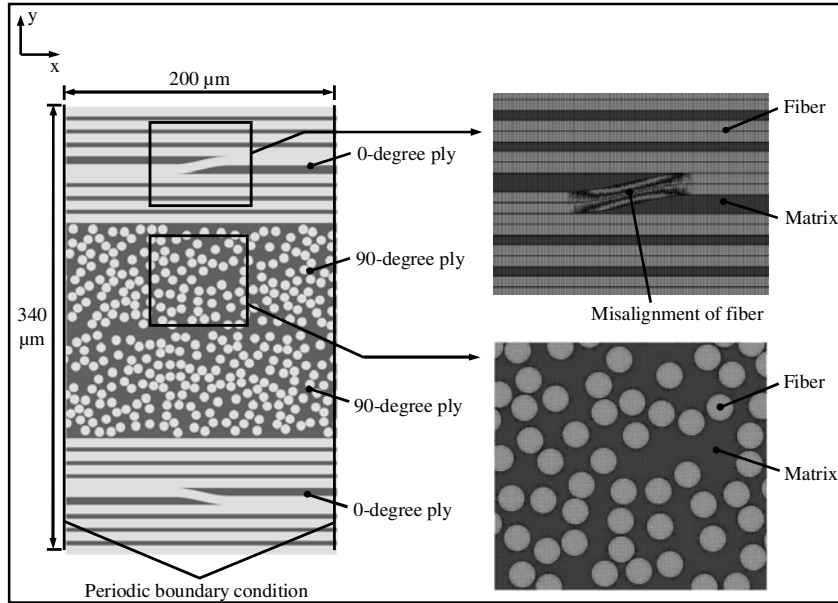


Fig. 1: Numerical Model of Cross-Ply Laminate

Table 1: Material Property of Fiber. Carbon Fiber AS4 (Hexcel Corp.) is Assumed [8]

Elastic modulus in fiber axial direction	225	GPa
Elastic modulus in transverse direction	15	GPa
In-plane Poisson's ratio	0.20	
In-plane shear modulus	15	GPa
Transverse shear modulus	7.0	GPa

Table 2: Material Property of Matrix. Epoxy Resin 3501-6 (Hercules Chemical Company, Inc.) is Assumed [8]

Elastic modulus	4.2	GPa
Poisson's ratio	0.34	
Yield stress	90	MPa

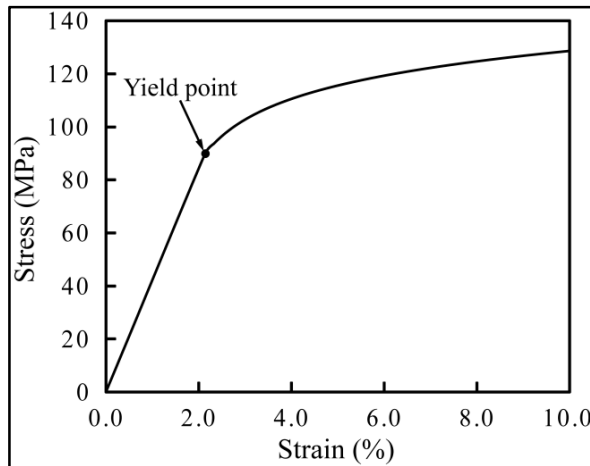


Fig. 2: Stress-strain Curve of Matrix

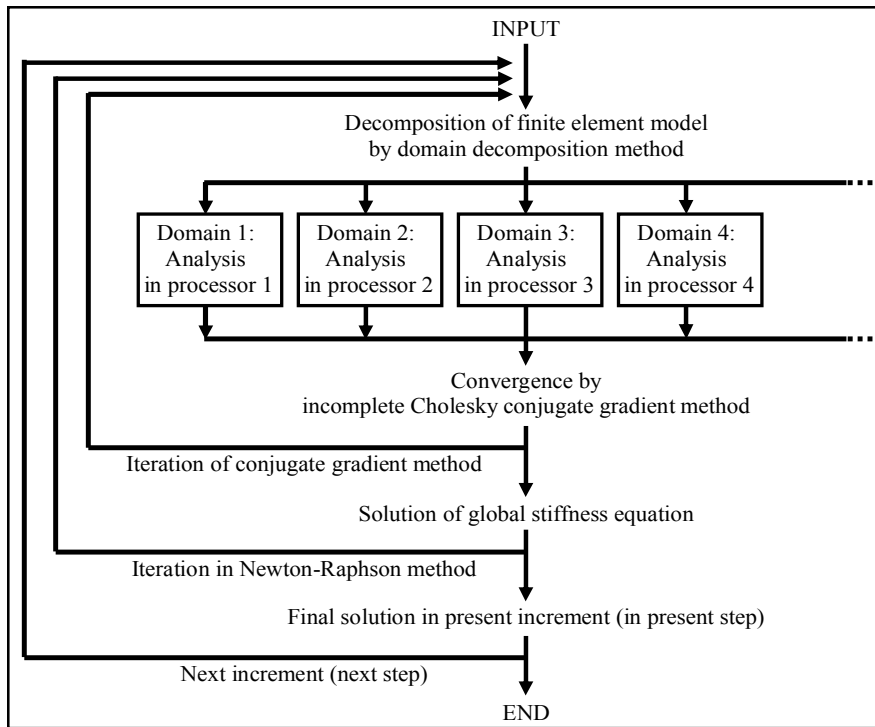


Fig. 3: Flowchart of Large-Scale Finite Element Analysis Using Domain Decomposition Method

Since the geometrical nonlinearity commonly affects the buckling phenomena of the materials, the geometrical nonlinear effect is incorporated in the analysis. The incremental analysis in the finite element analysis is conducted by the arc-length method. In the initial increment, the average applied strain to the material in x-direction is set to 0.004 %. The analysis is conducted until the average applied strain 6.0 %.

In this analysis, fourteen computers are connected. Each computer has six cores and twelve threads, and a total of 168 logical processors are unified to execute one calculation. The calculation is conducted continuously in 1200 hours. For the purpose of parallel computing, the domain decomposition method is applied, and for pre-conditioned conjugate gradient algorithm, incomplete Cholesky conjugate gradient method is applied. The numerical procedure of the analysis is shown in Fig. 3. The global finite element model representing the entire composite laminate which has complex internal structure including fibers and matrix is divided into domains, and the data of each domain is sent to each logical processor through communication between computers, and the calculation is executed in each logical processor. The calculation in each logical processor is independently conducted, and the convergence calculation is necessary to obtain the solution of the global finite element model. In order to improve the convergence calculation in the

analysis, incomplete Cholesky conjugate gradient method is applied which results in increase of the calculation speed and reduction of calculation time in each one increment. The incomplete Cholesky decomposition is for the pre-conditioning of the conjugate gradient algorithm and for the purpose of the improvement of the convergence in the numerical analysis. The domain decomposition and the convergence calculation is conducted in each iteration and each increment in the nonlinear finite element analysis, and after the solution of the global finite element model is obtained, the numerical analysis is proceeded to the next iteration in Newton-Raphson iteration, and when the convergence in Newton-Raphson iteration is obtained, the numerical analysis is proceeded to the next increment. The analysis is proceeded until the final fracture is formed in the entire material. Table 3 summarizes the calculation environment in this analysis. The authors produced fortran program for this analysis, and the analysis is conducted using this program.

Table 3: Calculation Environment

CPU	Intel core i7-3930K
Number of cores and threads	6 cores 12 threads
Memory	32 GB
Harddisk	1 TB
Number of computer	14
Total number of logical processors	168
Calculation time	1440 hours (60 days)
Programing language	Fortran

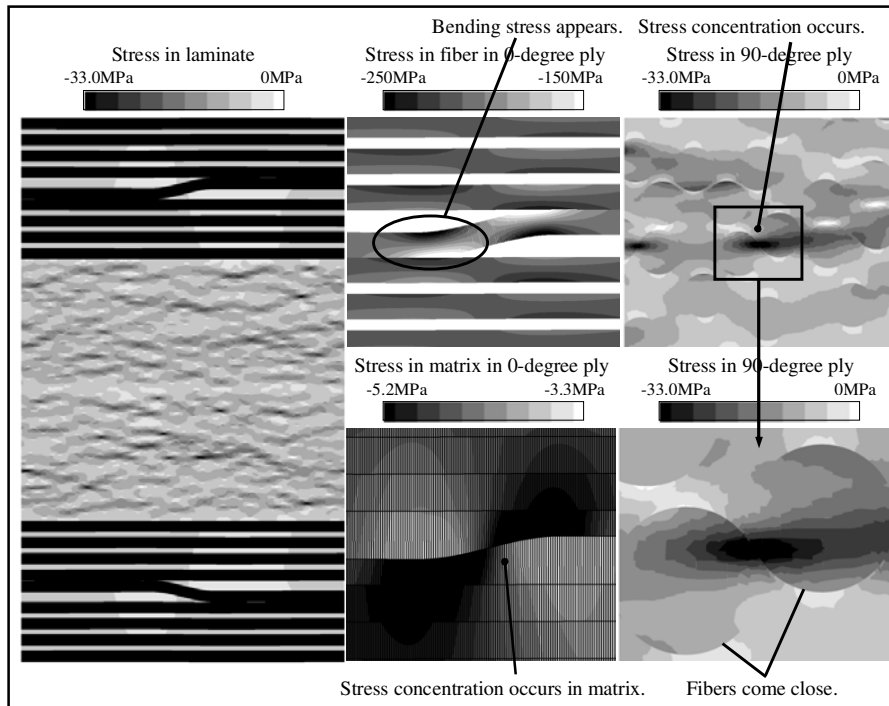


Fig. 4: Simulated Results of Stress Distribution at Average Applied Strain 0.1 %.

**SIMULATED RESULTS AND DISCUSSION**

Figure 4 shows the simulated results of stress distribution at average applied strain 0.1 %. In the laminated plate, particularly high stress distributes in reinforcement fibers in 0-degree plies, and a lot portion of the applied load to the laminate is supported by the fibers in 0-degree plies which are parallel to the loading direction. In the inside of 0-degree plies, stress disturbance occurs around the misalignment of fiber, and bending stress causes in the fiber which is increase of compressive stress in compressive deformation side and decrease of compressive stress in tensile deformation side, and the stress concentration occurs in matrix. In the inside of 90-degree plies, the stress concentration occurs in the material because of the randomness of the placement of fibers, and high stress appears in the area where fibers come close. When the applied load is increased, the stress state in matrix around the stress concentration area reaches the yield stress of matrix, and the yielding of matrix occurs in the local regions. Figure 5 shows the simulated results of deformation at applied strain 0.1 % and 4.3 %. At strain 0.1 %, the deformation of the laminate is close to the homogeneous compressive deformation, and the stress state in the material is close to the linear elastic state. At strain 4.3 %, the damage is formed in the laminate. In the simulated results, at strain 1.20% the damage initiates in the misalignment angle case, the failure load and the failure strain in simulated

results of load-strain curve laminate, and after this point the damage develops in the laminate. In this study, it is found that when the initial misalignment angle is changed and the numerical simulation is conducted for each change depending on the misalignment angle. It indicates that the failure load and failure strain change depending on the initial misalignment angle. Because of this, the failure strain is assumed to 1.20 %, and the value of initial misalignment angle is set so that the failure strain becomes 1.20 % in the simulated results.

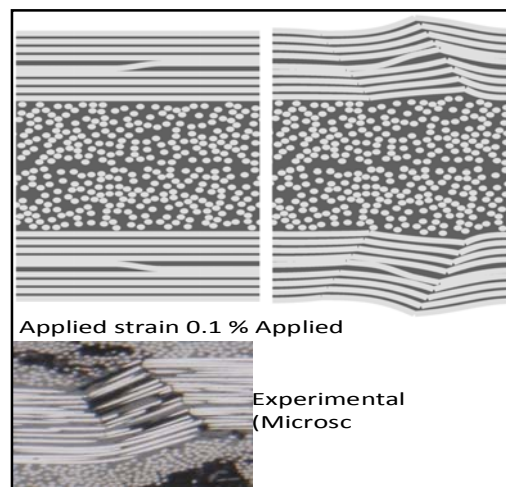


Fig. 5: Simulated Results of Deformation Before and after Damage Formation

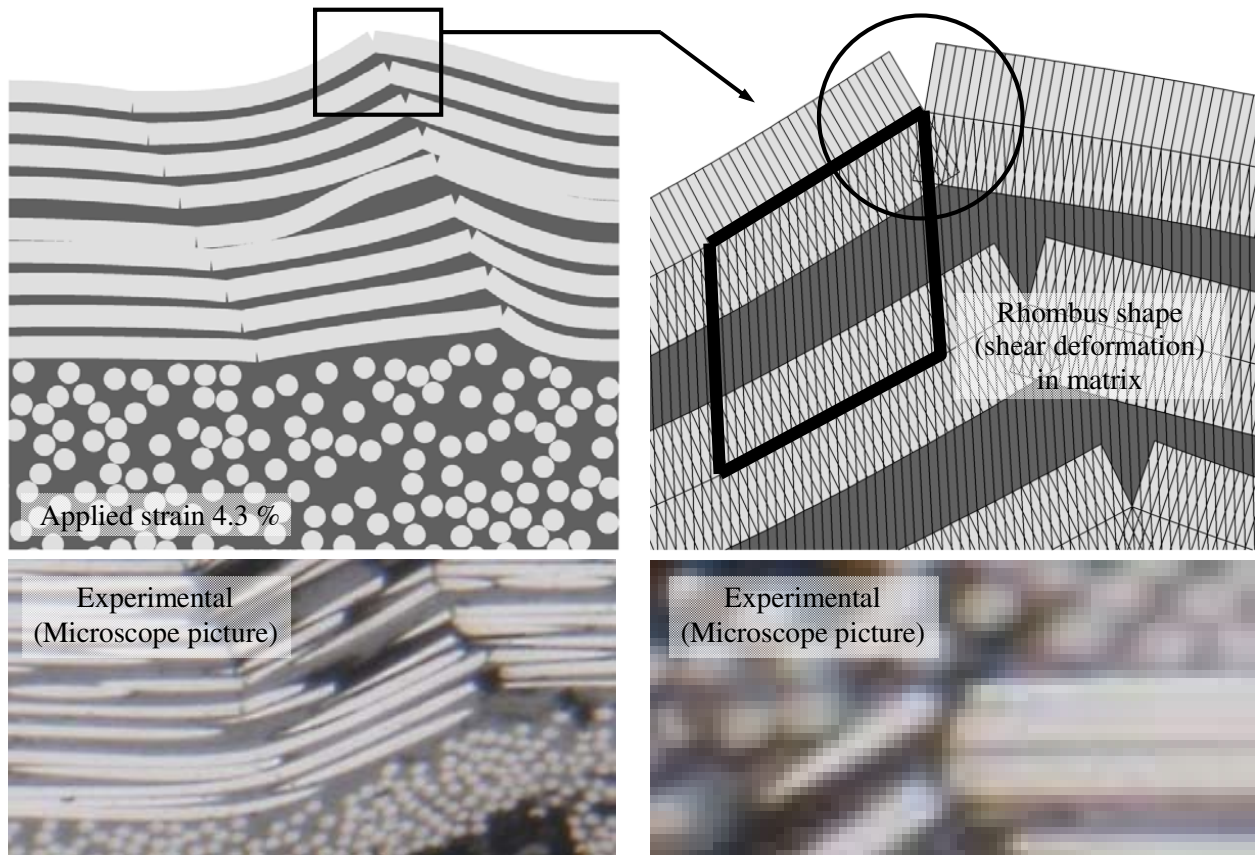


Fig. 6: Simulated Results of Deformation after Damage Initiation

Figure 6 shows the close-up view of the damage formed in the material. Fibers cause fracture because of the microscopic bending, and matrix causes shear deformation. The simulated damage is close to the microscope picture of the actual composite materials obtained in the experiment. The current simulation is considered to correspond with the actual material deformation. Figure 7 shows the simulated results of stress distribution in fibers and matrix with the deformation at strain 0.1 % and 4.3 %. After the damage is formed in the material, high stress distributes in both fibers and matrix.

## CONCLUSIONS

This study investigated the computer simulation for the internal fracture of cross-ply laminate of composite materials. The following remarks are obtained.

1. The reinforcement fibers in 0-degree plies are modeled by circle cross-section beam elements, and the cohesive elements are inserted in the connection of beam elements. The microscopic

fiber bending and breaking are successfully simulated in the numerical analysis.

2. The domain decomposition method is applied for the purpose of parallel computing, and incomplete Cholesky conjugate gradient method is applied for pre-conditioned conjugate gradient algorithm. The numerical analysis is successfully distributed to multiple processors, and the speed of numerical calculation is improved, and the large-scale model is enabled to be analyzed.
3. The simulated results show that in the initial state of the loading, the stress concentration occurs around the initial misalignment of fiber in 0-degree plies, and it also occurs around the area.

where fibers come close in 90-degree plies. At average applied strain 1.20 %, the fiber breaking damage initiates in 0-degree plies, and after this point the damage develops in the material. The simulated damage is close to the microscope picture of the actual composite materials obtained in the experiment. The current simulation is considered to correspond with the actual material deformation.

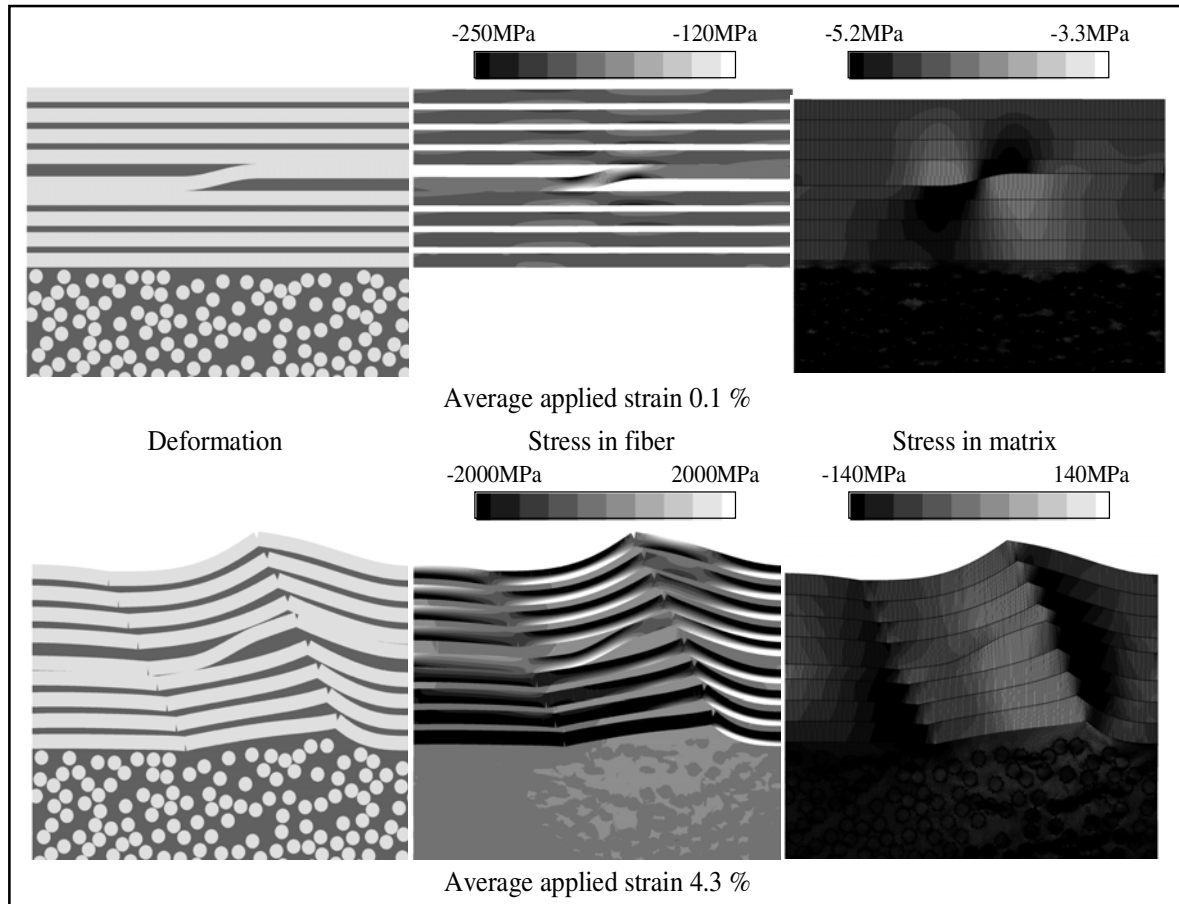


Fig. 7: Simulated Results of Stress Distribution before and After Damage Formation

## REFERENCES

- [1] Hinton, M.J. and Soden, P.D. (1998), "Predicting Failure in Composite Laminates: The Background to the Exercise", *Composites Science and Technology*, Vol. 58, pp. 1001–1010.
- [2] Schultheisz, C.R. and Waas, A.M. (1996), "Compressive Failure of Composites, Part I: Testing and Micromechanical Theories", *Progress in Aerospace Sciences*, Vol. 32, pp. 1–42.
- [3] Waas, A.M. and Schultheisz, C.R. (1996), "Compressive Failure of Composites, Part II: Experimental Studies", *Progress in Aerospace Sciences*, Vol. 32, pp. 43–78.
- [4] Llorca, J., González, C. and Molina-Aldareguía, J.M. *et al.* (2011), "Multiscale Modeling of Composite Materials: A Roadmap Towards Virtual Testing", *Advanced Materials*, Vol. 23, pp. 5130–5147.
- [5] Totry, E., González, C. and Llorca, J. (2008), "Failure Locus of Fiber-Reinforced Composites under Transverse Compression and Out-of-Plane Shear", *Composites Science and Technology*, Vol. 68, pp. 829–839.
- [6] Totry, E., González, C. and Llorca, J.L. (2008), "Prediction of the Failure Locus of C/PEEK Composites Under transverse Compression and Longitudinal Shear through Computational Micromechanics", *Composites Science and Technology*, Vol. 68, pp. 3128–3136.
- [7] Totry, E., González, C. and Llorca, J. (2008), "Influence of the Loading Path on the Strength of Fiber-reinforced Composites Subjected to Transverse Compression and Shear", *International Journal of Solids and Structures*, Vol. 45, pp. 1663–1675.
- [8] Soden, P.D., Hinton, M.J. and Kaddour, A.S. (1998), "Lamina Properties, lay-up Configurations and Loading Conditions for a Range of Fibre-reinforced Composite Laminates", *Composites Science and Technology*, Vol. 58, pp. 1011–1022.